

CATEGORY	Page
1- Metal-Organic Framework Cu ₂ (OBA) ₂ (BPY) as efficient catalyst for C–O bond formation via oxidative cross-coupling reaction of benzaldehyde and 1,4-dioxane - Huynh Quoc Thai, Nguyen Thi Ngoc Tran, Ha Thanh My Phuong, Dang Huynh Giao, Doan Hoai Son, Phan Thanh Son Nam	2
2- Well-defined rod coil diblock copolymers based on poly(3-hexylthiophene) and poly(methyl methacrylate) via metal-free atom transfer radical polymerization - Nguyen Huu Tam, Tran Minh Hoan, Truong Thu Thuy, Nguyen Tran Ha	10
3- Study the effects of reaction parameter on degradation of janus green B by using nano zinc oxide loaded on activated carbon - Pham Quang Minh, Nguyen Thi Van, Vu Anh Tuan	16
4- Improved photocatalytic activity of ZnO by modification with CuO - Nguyen Van Kim, Nguyen Thi Viet Nga, Tran Thi Thanh Cam, Pham Thi Trinh, Nguyen Thi Lan, Nguyen Van Nghia, Tran Thi Thu Phuong, Vo Vien	23
5- Study on preparation of TiO ₂ Sol using TiCl ₄ as a Precursor for catalytic applications - Pham Minh Tu, Do Manh Hung, Au Thi Hang, Nguyen Bich Ngoc, Vu Thi Thu Ha	30
6- Synthesis of TiO ₂ -V ₂ O ₅ composites for photocatalytic degradation of methylene blue under visible light irradiation - Le Thi Thanh Thuy, Nguyen Anh Thoang, Le Si	36
7- Synthesis and photocatalytic activity of magnetic Fe ₃ O ₄ -ZnO composite - Tran Thi Phuong Hong, Nguyen Thi Hong Nhung, Nguyen Van Kim, Nguyen Thi Viet Nga, Vo Vien	43
8- Synthesis of Fe-MIL-101 material and evaluation of photocatytic activity under visible light - Huynh Thi Minh Thanh, Tran Ngoc Tuyen, Dinh Quang Khieu	49
9- Study on phenol adsorption onto Fe-MIL101 in aqueous solution - Tran Ngoc Tuyen, Nguyen Duc Vu Quyen, Ha Thi Thu Hoai, Nguyen Thanh Tan, Huynh Thi Minh Thanh	54
10- Study on the preparation of activated carbon from coffee husk toward the adsorption of dye in aqueous solution - Ta Huu Son, Le Van Khu, Luong Thi Thu Thuy	61
11- Study on building Sylop graph of H ₂ S after activated carbon layer - Bui Van Tai, Hoang Trung Hieu	67
12- Research on column adsorption of Pb ²⁺ by hydroxyapatite granules - Le Thi Duyen, Le Thi Phuong Thao, Do Thi Hai, Vo Thi Hanh, Pham Tien Dung, Pham Thi Nam, Nguyen Thi Thom, Cao Thi Hong, Le Thi Sau, Dinh Thi Mai Thanh	71
13- Synthesis, structural characterization and adsorption capacity of H-δ-MnO ₂ - Dang Thi To Nu, Nguyen Thi My Duyen, Cao Van Hoang, Nguyen Thi Lieu, Nguyen Phi Hung	80
14- Study on catalyst based on CuO modified with Boron applied for selective oxidation of propylene to acrolein - Pham Thi Mai Phuong, Vu Quoc Quan, Le Minh Thang	86
15- Immobilization of glucose oxidase onto core-shell structure materials Fe ₃ O ₄ NP@SiO ₂ and testing it's catalytic activity - Hoang Ngoc Anh Nhan, Nguyen Ba Trung	92
16- Preparation of bio-char from Acacia Sawdust and Sugarcane bagasse for Solid acid Catalyst Fabrication - Le Quang Dien, Nguyen Trung Thanh, Nguyen Thanh Long, Nguyen Thi Nhi, Nguyen Minh Chau, Nguyen Hoang Chung	98
17- Synthesis of alkanolamide nonionic surfactant using used cooking oil - Tran Thi Thanh Ngoc, Nguyen Thanh Nhat, Bui Tan Nghia	105
18- Mathematical model and simulation of a heterogeneous catalytic reactor for reforming process of heavy gasoline - Nguyen Huu Duong, Vu Hong Thai	111
19- Synthesis of adsorbed materials from Bentonite Co Dinh – Thanh Hoa, Application for removal of ammonium in water treatment - Truong Quoc Anh, Mai Van Tien, Bui Thi Thu	116
20- Study on preparation of nano-ZIF-67 in ethanol - Le Van Duong, Dinh Quang Toan, Pham Thu Huong, Le Ngoc Duong, Nguyen Thi Xuan, Ninh Thi Phuong, Ta Ngoc Don	122
21- Hydropolymerization of ethylene - A future manufacture of fuel production - Nguyen Quang Minh, Dao Quoc Tuy	128



Vietnam Journal of Catalysis and Adsorption

Tạp chí xúc tác và hấp phụ Việt Nam

<http://chemeng.hust.edu.vn/jca/>

Study the effects of reaction parameter on degradation of janus green B by using nano zinc oxide loaded on activated carbon

Pham Quang Minh¹, Nguyen Thi Van², Vu Anh Tuan^{2,*}

¹ Physical and chemical Department, National Institute for Control of Vaccine and Biologicals, Vietnam

² School of Chemical Engineering, Hanoi University of Science and Technology, Hanoi, Vietnam

*Email: tuan.vuanh@hust.edu.vn

ARTICLE INFO

Received: 03/7/2018

Accepted: 21/7/2018

Keywords:

Photodegradation, Zinc Oxide, Activated Carbon, Rice Husk, Janus Green B

ABSTRACT

In this study, zinc oxide nano particles loaded on activated carbon (ZnO/AC) has been successfully prepared for degradation of Janus Green B (JGB) under low UV light intensity. The activated carbon (AC) was synthesized from rice husk by two steps calcination at 800 °C, ZnO/AC was synthesized by hydrothermal method with the assistant of HMTA. As-prepared samples were characterized by XRD, FE-SEM, N₂ adsorption/desorption. The effects of operational parameters on the photo-degradation reaction progress, including catalyst dosage, initial dye concentration, initial pH value and the addition of inorganic anions were investigated in detail. In addition, the photodegradation rate of JGB on composite was evaluated by using the pseudo-first-order model.

Introduction

Urbanization and heavy industrialization caused our environment polluted seriously. It is a global menace to man's health and the magnitude of it is increasing day by day. Especially, wastewater released from dyeing industries is one of the main pollution sources. Up to now the environmental remediation technologies, including adsorption, biological oxidation, chemical oxidation, and incineration, have been used to treat all types of organic and toxic wastewater [1]; therein one of the typical environmental remediation methods is chemical degradation.

In chemical methods, semiconductor photocatalysis has emerged as one of the most promising processes for waste water treatment as compared to other conventional techniques [2]. Because it can be completely oxidized, easy to operation and low cost.

As one of the most important semiconductor photocatalysts, ZnO has attracted considerable interest

because of its high photosensitivity and stability [3]. However, the use of ZnO powders has many difficult problems such as separating the powder from the solution after completing the reaction, aggregation of particles in suspension at high loading, and difficulty in application to continuous flow systems [4]. Fortunately, these disadvantages of ZnO are avoidable through the process of surface modification and this can be achieved by coating ZnO particles by support materials like activated carbon and silica.

Rice husk is a by-product of the rice milling process, which is the outer covering of the rice grain, most of the rice husk is usually either dumped or burned in open spaces, thus causing damage to the land and environmental pollution. Much efforts have been made to utilize the rice husk including as an alternative fuel for energy production, production of activated carbon (AC) and as a raw material for manufacture of industrial chemicals based on silica and silicon compounds [5]. In there, AC has porous structure, high

surface area and low cost so it is considered a great material for catalyst and adsorption of metal ions and organic molecules in both gas and aqueous phases.

Considering the study on degradation of dyes in aqueous solution, the ZnO/AC was prepared successfully by hydrothermal method using rice husk as an activated carbon source. The batch reaction was conducted to study the degradation of JGB on catalyst. The effects of catalyst dosage initial dye concentration, initial pH value, and the addition of inorganic anions were investigated in detail.

Experimental

2.1. Materials

Janus Green B (JGB) was purchased from Sigma-Aldrich, the chemical structure and some of the important physicochemical properties of JGB are presented in Figure 1. Rice husk was obtained from Thai Binh province. Zinc acetate ($\text{Zn}(\text{CH}_3\text{COO})_2 \cdot 2\text{H}_2\text{O}$, 99%), hexamethylene tetramine-HMTA ($\text{C}_6\text{H}_{12}\text{N}_4$, 99%), sodium hydroxide (NaOH, 99.5 %) and liquid ammonia (NH_3 , 28%) were obtained from China. All the chemicals were used without any purification and distilled water was used throughout the experiments.

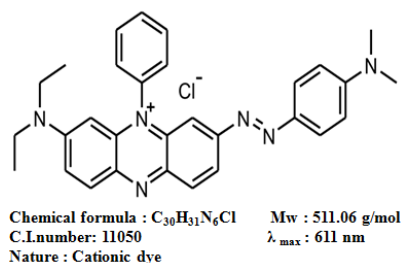


Figure 1. The chemical structure and physical properties of JGB [6].

2.2. Preparation of activated carbon from rice husk

The preparation of activated carbon is presented in Figure 2. Rice husk obtained from Thai Binh was washed with distilled water to remove soil and dust and then dried at 100 °C for 24h. The dry rice husk was carbonized at 400 °C for 2h at a heating rate of 5° C/min to produce charcoal. Subsequently, charcoal was crushed by pestle and mortar, the charcoal power was then impregnated with 4M NaOH at weight ratio NaOH:charcoal of 1:1. The mixture was dried at 100 °C for 24h. The obtained powder was calcined in a furnace under N_2 flow by 2 steps: (1) temperature

increased from room temperature to 400 °C at 8°C/min and remained temperature for 1h; (2) the temperature increased from 400 °C to 800 °C at 10 °C/min and remained temperature for 2h. After cooling, the samples was washed with distilled water until pH reached neutral, then dried at 100 °C for 24h. Finally, the activated carbon was obtained and used for further studied.

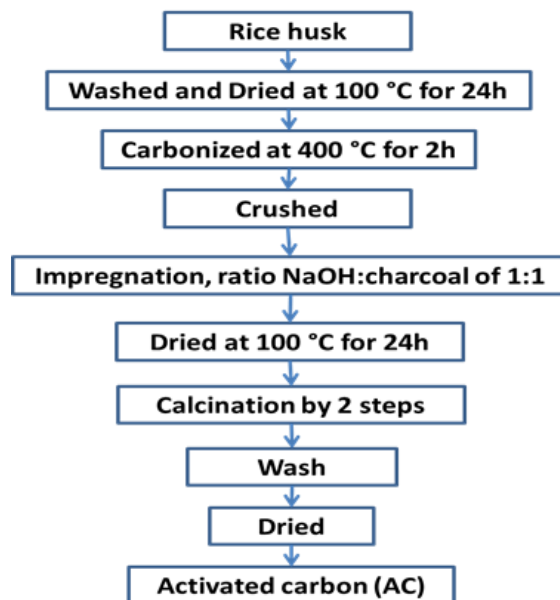


Figure 2: Preparation procedure of activated carbon

2.3. Preparation of ZnO/AC

ZnO/AC composite was prepared by hydrothermal method. Typically, 2.19 g zinc acetate and 0.7 g HMTA were dissolved in 100 mL of distilled water to form clear solution. Subsequently, the pH of solution was adjusted to 8.0 by using liquid ammonia under stirring. After 5 min of stirring, an amount of AC (10 wt.%) was added to above solution. The suspension was stirred vigorously for 5 min and then transferred into teflon-lined autoclave and heated at 150 °C for 24h. The collected solids were washed several times with distilled water, dried at 80 °C for 24 h to obtained back powder, this sample, before calcination, was denoted as ZnO/ZHC/AC. Finally, the powder was calcined in N_2 at 400 °C for 2 hours. The obtained grey powder was denoted as ZnO/AC. For comparison, pure ZnO was prepared by the same procedure to ZnO/AC without adding the AC into the synthesis process.

2.4. Characterization

The crystalline phase of samples was investigated by

X-ray power diffraction. XRD patterns were obtained by using Bruker D8 Ax XRD-diffractometer (Germany) with Cu K α irradiation (40kV, 40 mA). The 2 θ ranging from 10 to 80 ° was selected to analyse the crystal structure. The morphology of the samples was observed by field emission scanning electron microscopy (FE-SEM, JEOL-7600F). The textural properties were measured via N₂ adsorption/desorption isotherms using a Micromeritics (Gemini VII analyzer). The specific surface area, pore volume and pore diameter were obtained by using the Brunauer-Emmett-Teller (BET) method.

2.5. Photocatalytic test

The photodegradation of JGB on catalyst was carried out by batch test. Typically, 50 mg of catalyst was added into a 250 mL glass beaker containing 100 mL of JGB 10 mg/L. The mixed solution was ultrasonicated for 10 min and then the UV lamp (8W halogen lamp) was switched on. The catalyst powders were stirred at a constant rate entire reaction process. At given time intervals of 10 min, 2 mL of samples were withdrawn from the suspension and then filtered by a syringe filter (0.45 μ m PTFE membrane) to remove the catalyst. The dye concentration of the filtrate was analyzed by a UV-Vis spectrophotometer (Agilent 8453) at the maximum absorbance wavelength 611 nm.

$$\text{Degradation efficiency (\%)} = \frac{C_0 - C_t}{C_0} \cdot 100\% \quad (1)$$

The photodegradation rate of JGB on catalysts can be evaluated by using the pseudo-first-order model as follow:

$$\ln \frac{C_0}{C_t} = kt \quad (2)$$

Where C_0 and C_t are the concentration of JGB at initial ($t = 0$) and time t (min), respectively. k is the pseudo first-order rate constant. The k value was calculated from the slope of the $\ln (C_0/C_t) - t$ plots.

Results and discussion

3.1. Characterization of samples

Characterizations of materials are presented in Figure 3. Figure 3 (a), AC was observed with the different shapes and had a rough surface. In the sample before calcination, ZnO/ZHC with rod-like shape growth on the surface of AC, the growth directions of the nanorods appeared relatively random on none-planar substrates. The bulk shape had average length and width of approximately 1 μ m and 500 nm, respectively, in Figure 3(b). As seen in Figure 3(c), ZnO had the similar sharp to pure ZnO and it highly dispersed on surface of AC. The ZnO particles size was in range of 20-30 nm. These results revealed that the sharp of ZnO after calcination was different from that before calcination. For the ZnO/ZHC/AC sample, the peaks of ZnO were also observed in XRD result. In addition, the lattice plans (200) observed could be ascribed to zinc hydroxide carbonate (ZHC) (JCPDS 19-1458) [7,8]. The sample after calcinations at 400°C for 2h (ZnO/AC) included both diffraction peaks of AC and ZnO, and no other impurity peaks were observed. Some textural properties of material obtained by BET method were shown in Table 1. These results are consistent with previous publications [9,10].

Table 1: Textural properties of AC, ZnO, ZnO/ZHC/AC and ZnO/AC composites.

Samples	S_{BET} (m ² /g)	Pore volume (cm ³ /g)	Average pore size (nm)
AC	1062	1.06	3.58
ZnO	24	0.28	47.9
ZnO/ZHC/AC	191	0.29	6.29 [11]
ZnO/AC	251	0.41	10.24

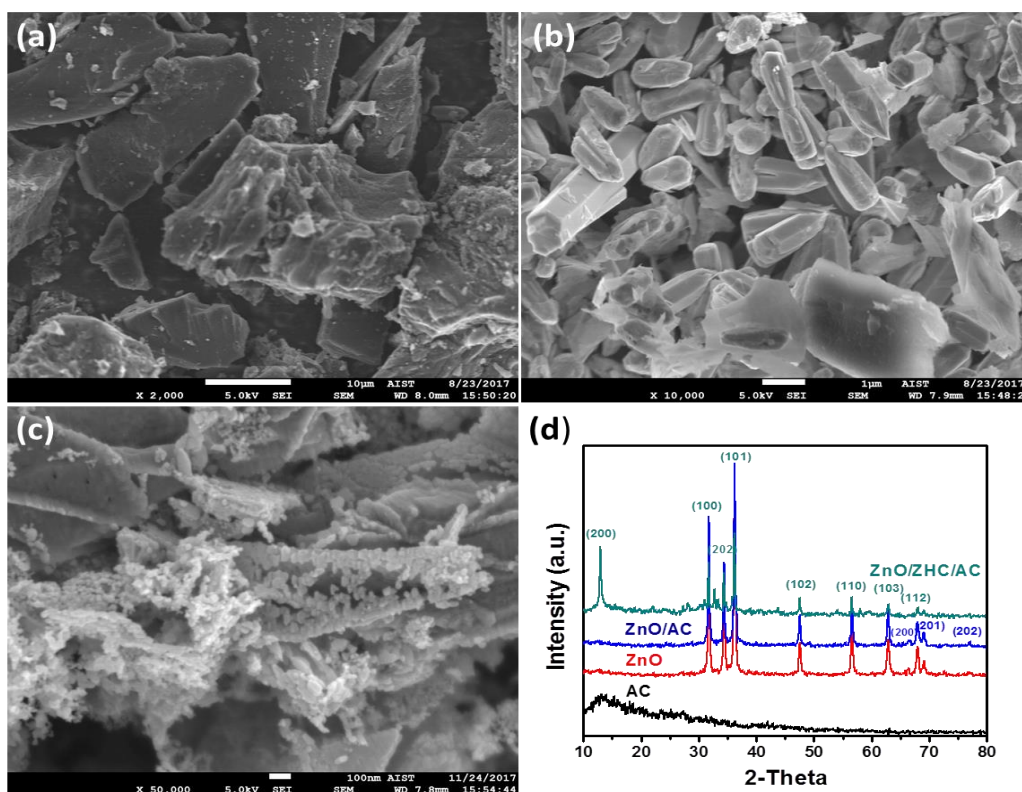


Figure 3: (a), (b) and (c) SEM images of AC, ZnO/ZHC/AC and ZnO/AC; (d) XRD patterns of AC, ZnO, ZnO/ZHC/AC and ZnO/AC composites.

suspension is increased, the short wave tail photons are not able to enter the reaction mixture and a decrease in UV light penetration as a result of increased scattering effect [12], the degradation efficiency decreased.

3.2. Effect of reaction parameters

3.2.1. Effect of dosage catalyst

Effect of dosage catalyst on the degradation of dye is shown in Figure 4. In initial 35 min, the degradation rate and degradation efficiency of JGB increased when dosage catalyst increased from 0.025 to 0.1 g. However, the degradation efficiency was observed to be slightly degraded for dosage catalyst of 0.1 g after 35 min. The reaction rate in 60 min were 0.050, 0.083, 0.083, 0.109 and 0.080 min^{-1} for 0.025, 0.05, 0.075 and 0.1 g dosage of ZnO/AC respectively. The degradation of JGB reached 100% for dosage catalyst of 0.075 g, as seen in Table 2.

The effect of catalyst dosage on degradation process can be explained by the following reasons: the increasing catalyst dosage results in an increase in the number of active sites that are available at the surface of catalyst, so the density of catalyst particles in the area of illumination is improved. However, when dosage of catalyst exceeds the limit value leading the

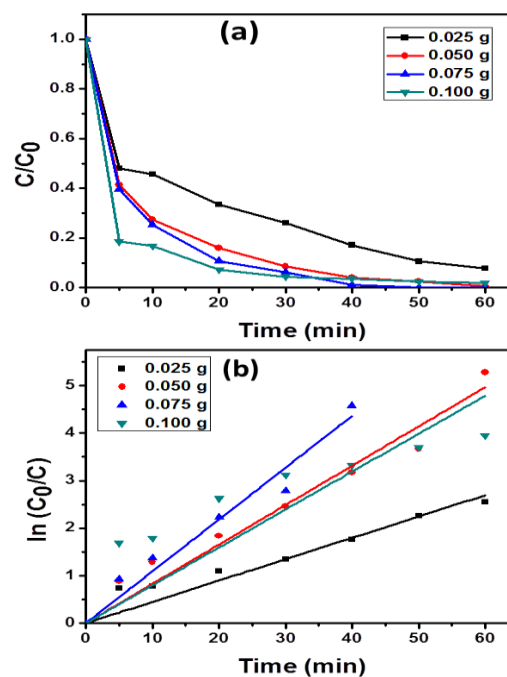


Figure 4: (a) Effect of ZnO/AC dosage on the degradation of JGB under UV-irradiation and (b) the kinetic curves.

Table 2: Kinetic parameters for photodegradation of JGB at different dosages catalyst.

Dosage catalyst	k (min ⁻¹)	R ²	Degradation efficiency (%)
0.025 g	0.050	0.95	92.17
0.050 g	0.083	0.97	99.49
0.075 g	0.109	0.97	100.0
0.100 g	0.080	0.83	98.08

3.2.2. Effect of dye concentration

In order to examine the impact of various dye concentrations on the photocatalytic degradation, the experiments were conducted by varying the concentration of JGB from 5 to 20 mg/L. While other condition, dosage catalyst, reaction temperature, and initial pH were remained at constant, 0.05 g, 25 °C and 6.0, respectively. The result is presented in Figure 5. It was found that the JGB was strongly degraded with high degradation rate at JGB concentration of 5 mg/L. The increase in JGB concentration led the decrease in degradation efficiency. The degradation efficiency for concentration of 5, 10, 15 and 20 mg/L were 100, 99.49, 88.23 and 83.40 %, respectively, in 60 min of reaction. The degradation rate also was decreased when concentration of JGB increased. The k values were calculated and listed in Table 3.

This effect can be interpreted by the following reasons: When increases of JGB concentration, the photons get intercepted before they can reach the catalyst surface, so the generation of $\bullet\text{OH}$ and $\bullet\text{O}_2^-$ radical decreases, meaning photodegradation efficiency of JGB solution decreases and a large number of JGB molecules along with the intermediates generated may compete for the constant total active sites available for adsorption at a fixed concentration of ZnO/AC [13]. Additionally, with increase in the initial dye concentration, the solution becomes more intensely coloured and the path length of photons entering into the solution decreases [14], thus the absorption of photos by the catalysts decreases, and consequently the degradation rate is reduced.

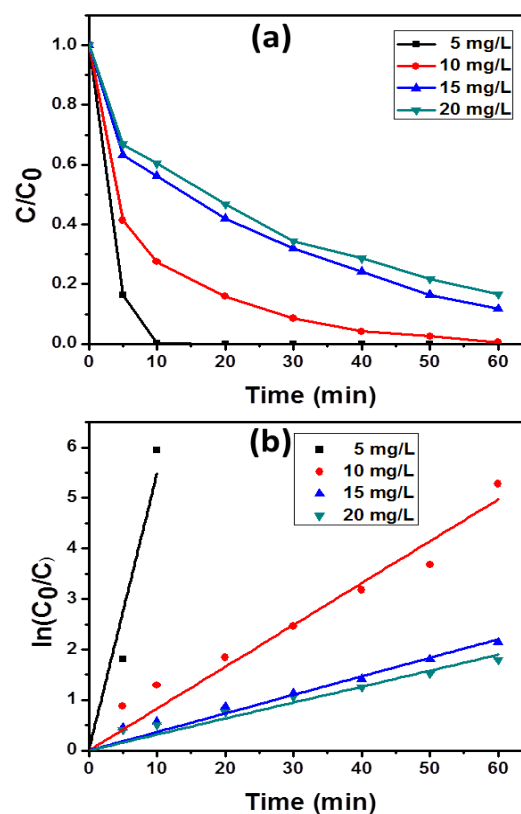


Figure 5: (a) Effect of initial dye concentration on the degradation of JGB and (b) the kinetic curves.

Table 3: Kinetic parameters for photodegradation of JGB at different dye concentrations.

Samples	k (min ⁻¹)	R ²	Degradation efficiency (%)
5 mg/L	0.548	0.92	100.0
10 mg/L	0.083	0.97	99.49
15 mg/L	0.037	0.97	88.23
20 mg/L	0.032	0.97	83.40

3.2.3. Effect of solution pH

One of the most important parameters in photocatalytic degradation reaction is the solution pH, thus the effect of initial solution pH to remove dye was examined and the result is presented in Figure 5. The effect of initial solution pH on degradation of JGB was investigated in the pH range of 3–12, at the 0.05 g catalyst dosage, 10 mg/L dye concentration, and reaction temperature of 25 °C. The pH of the reaction solution was adjusted before light irradiation and it was not controlled during the reaction. The obtained results indicated that the degradation of Janus Green B was significantly influenced by the solution pH. The

degradation percentages for the different initial pH values were presented in Table 4. The alkaline condition, pH value was larger than 11, was very beneficial to the photocatalytic oxidation of Janus Green B dye. The reaction rate of JGB at different pH values are presented in Table 4. The zero-point charge (pH_{ZPC}) for ZnO is 9.0^[15]. At low pH ($pH < pH_{ZPC}$), ZnO surface is positively charged. At above pH ($pH > pH_{ZPC}$), ZnO surface is negatively charged by OH^- ion. The presence of large quantities of OH^- ions on the particle surfaces as well as in the reaction medium favors the formation of $\bullet OH$ radicals, therefore the degradation efficiency increases. Whereas, ZnO can be partially dissolved in acidic medium ($pH < 6$), leading the decrease in degradation efficiency.

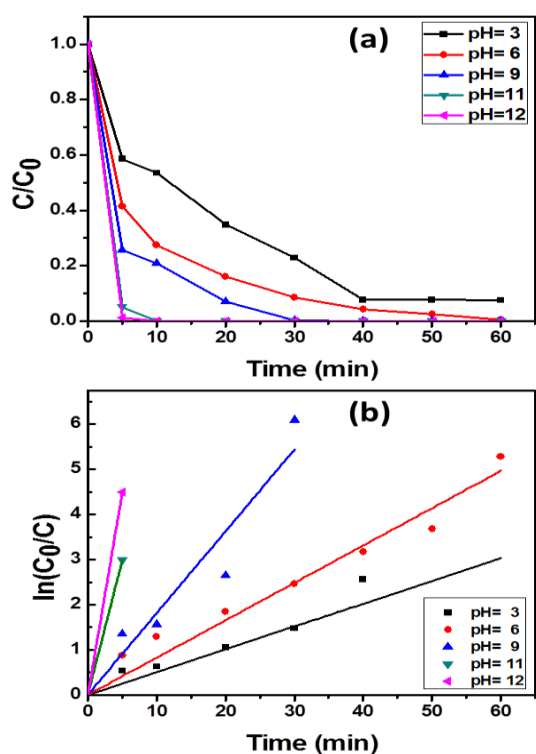


Figure 6: (a) Effect of initial pH on degradation of JGB and (b) the kinetic curves

Table 4: Kinetic parameters for photodegradation of JGB at different initial pH values

Samples	k (min^{-1})	R^2	Degradation efficiency (%)
pH= 3	0.051	0.95	92.56
pH= 6	0.083	0.97	99.49
pH= 9	0.181	0.92	100.0
pH=11	0.598	1.00	100.0
pH=12	0.899	1.00	100.0

3.2.4. Effect of inorganic anions on photocatalytic degradation of JGB dye

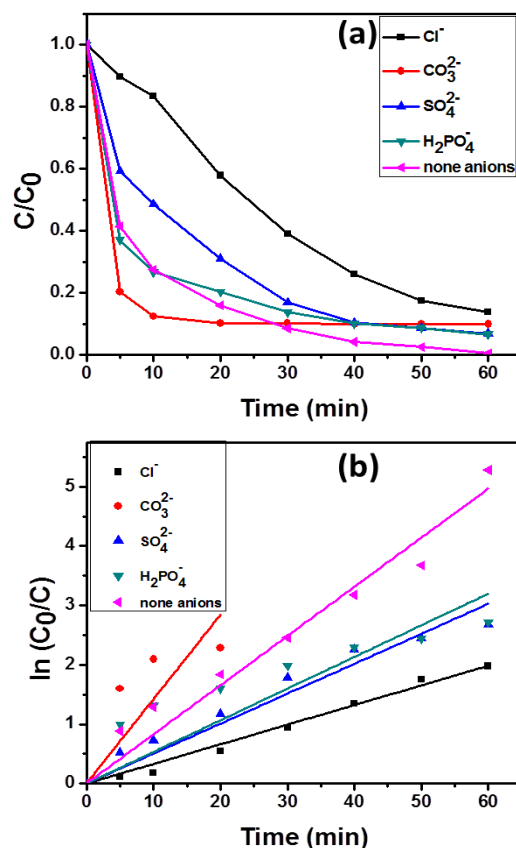


Figure 7: (a) Effect of inorganic anions on photocatalytic degradation of JGB at reaction conditions: 0.05 g dosage catalyst, 10 mg/L initial concentration of JGB, initial pH of 6.0, 2 g/L concentration of anion and (b) the kinetic curves

Wastewater from dyeing industry usually contains either organic contaminants or abundant inorganic anions such as sulfate and carbonate [16]. Thus, it is necessary to investigate the impact of these ions on the photocatalytic process. The influence of added inorganic anions on the removal of JGB dye was studied at 0.2 g/L concentration and displayed in Figure 7. It can be found that all of added inorganic anions had an inhibition effect on the photocatalytic process and lowered the photocatalytic degradation rate of JGB dye. At the presence of $H_2PO_4^-$, SO_4^{2-} , CO_3^{2-} and Cl^- the degradation efficiency decreased from 99.49 to 93.40, 93.11, 90.17 and 86.19%, respectively, as seen Table 5. Since the common cation of all the added inorganic anions (Na^+) is inert; hence, only anions are involved in the retardation effect. The degradation efficient of JGB was inhibited may be due

to a competitive adsorption of these anions and the target organic substance at the surface of catalyst, leading to blockage of the active sites at the surface of photocatalyst and these inorganic anions cover the ZnO surface, which prevents the exposure of the JGB molecule to ZnO. Additionally, these negatively charged inorganic anions can react with holes (h^+) and hydroxyl radicals ($\bullet OH$) to produce less-reactive species due to their lower oxidation potentials, and those inorganic anions behaved similar to h^+ and $\bullet OH$ scavengers, which is a great impediment to the progress of the reaction.

Table 5: Kinetic parameters of photodegradation of JGB

Samples	k (min ⁻¹)	R ²	Degradation (%)
none anions	0.083	0.97	99.49
Cl ⁻	0.033	0.99	86.19
CO ₃ ²⁻	0.142	0.69	90.17
SO ₄ ²⁻	0.050	0.96	93.11
H ₂ PO ₄ ⁻	0.053	0.85	93.40

Conclusion

In summary, the ZnO/AC catalyst was successful prepared from rice husk for photodegradation of JGB from aqueous solution. The JGB solution with a concentration of 10 mg/L and initial pH = 12 was degraded up to 100.0 % at dosage catalyst of 0.05 g within 60 min under UV irradiation. Alkaline condition was beneficial to the degradation of JGB solution. The presence of inorganic ions significantly caused the inhibiting degradation of JGB. These results gave an opening and promising application of this material in wastewater treatment.

Acknowledgments

This research is funded by Vietnamese Ministry of Education and Training under grant number B2017-BKA-53.

References

- Gholamreza Moussavi, Maryam Mahmoudi, Removal of azo and anthraquinone reactive dyes from industrial wastewaters using MgO nanoparticles, *Journal of Hazardous Materials*, 2009, 168, 806-812.
- Sini Kuriakose, Vandana Choudhary, Biswarup Satpati, Satyabrata Mohapatra, Facile synthesis of Ag-ZnO hybrid nanospindles for highly efficient photocatalytic degradation of methyl orange, 2014.

- Zhi-gang Jia, Kuan-kuan Peng, Yan-hua Li, Rong-sun Zhu, Preparation and photocatalytic performance of porous ZnO microrods loaded with Ag, *Transactions of Nonferrous Metals Society of China*, 2012, 22, 873-878.
- Narayanasamy Sobana, Manickavasakam Muruganandam, Meenakshisundaram Swaminathan, Characterization of AC-ZnO catalyst and its photocatalytic activity on 4-acetylphenol degradation, *Catalysis Communications*, 2008, 9, 262-268.
- A. Kumar, K. Mohanta, D. Kumar, O. Parkash, Properties and industrial applications of rice husk: A review, 2011.
- Vu Van Tu, Phan Thi Yen, Nguyen Anh Vu, Tran Thi Thuy, Vu Anh Tuan, A Facile Precipitation Method to Synthesize Submicrometer-Size MgO for Removing Janus Green B from Aqueous Solution, *Tạp chí Khoa học và Công nghệ*, 2016, 115, 6.
- Yu Miao, Haijiao Zhang, Shuai Yuan, Zheng Jiao, Xuedong Zhu, Preparation of flower-like ZnO architectures assembled with nanosheets for enhanced photocatalytic activity, *Journal of Colloid and Interface Science*, 2016, 462, 9-18.
- Aihua Lei, Baihua Qu, Weichang Zhou, Yanguo Wang, Qinglin Zhang, Bingsuo Zou, Facile synthesis and enhanced photocatalytic activity of hierarchical porous ZnO microspheres, *Materials Letters*, 2012, 66, 72-75.
- J. N. Hasnidawani, H. N. Azlina, H. Norita, N. N. Bonnia, S. Ratim, E. S. Ali, Synthesis of ZnO Nanostructures Using Sol-Gel Method, *Procedia Chemistry*, 2016, 19, 211-216.
- Giana G. Lenzi Lariana N. B. Almeida, Juliana M. T. A. Pietrobelli, Onelia A. A. dos Santos, Performance Evaluation of Catalysts of ZnO in Photocatalytic Degradation of Caffeine Solution, *Engineering Transactions*, 2017, 57.
- Phung Thi Hoai Anh, Nguyen Thi Van, Vu Anh Tuan, Preparation of zinc oxide/zinc hydroxide carbonate on activated carbon composites for degradation of janus green B, *Vietnam Journal of Catalyst and Adsorption*, 2018, 7, 5.
- Ahed Zyoud, Amani Zu'bi, Muath Helal, Daehoon Park, Guy Campet, Hikmat Hilal, Optimizing photo-mineralization of aqueous methyl orange by nano-ZnO catalyst under simulated natural conditions, 2015.
- M. A. Behnajady, N. Modirshahla, R. Hamzavi, Kinetic study on photocatalytic degradation of C.I. Acid Yellow 23 by ZnO photocatalyst, *Journal of Hazardous Materials*, 2006, 133, 226-232.
- B. Krishnakumar, M. Swaminathan, Solar photocatalytic degradation of Naphthol Blue Black, *Desalination and Water Treatment*, 2013, 51, 6572-6579.
- Fan Zhang, Xin Chen, Fenghuang Wu, Yuefei Ji, High adsorption capability and selectivity of ZnO nanoparticles for dye removal, *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, 2016, 509, 474-483.
- Chantal Guillard, Eric Puzenat, Hinda Lachheb, Ammar Houas, Jean-Marie Herrmann, Why inorganic salts decrease the TiO₂ photocatalytic efficiency, 2005.